

SPECIFICATION CONTROL DRAWING

55FA0511

| | | | | | |
|---|--|------|---------|----------|---|
| TITLE | CABLE, ELECTRIC, FILTER LINE - ELECTROLOSS, COMPONENT WIRE | Date | 7-23-10 | Revision | J |
| This specification sheet forms a part of the latest issue of Raychem Specification 55F. | | | | | |

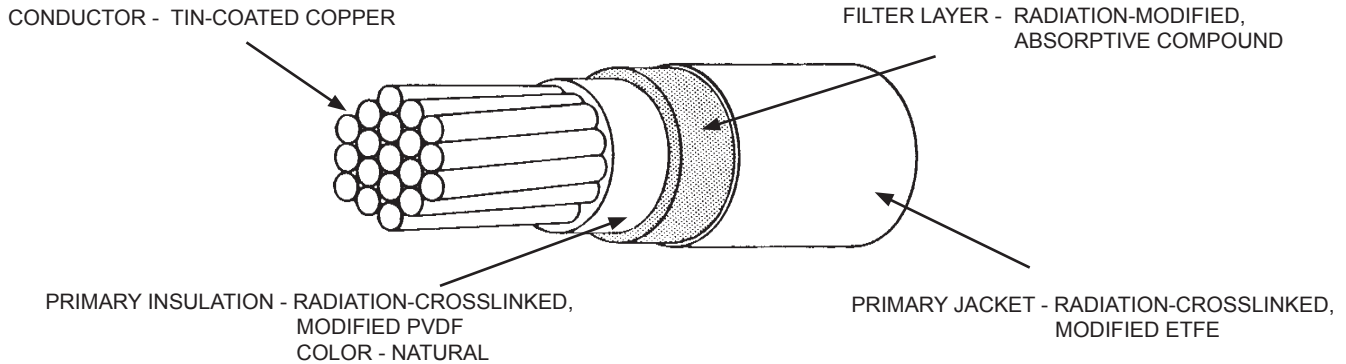


TABLE I. CONSTRUCTION DETAILS

| PART NUMBER 1/ | WIRE SIZE (AWG) | CONDUCTOR STRANDING (number x AWG) | DIAMETER OF STRANDED CONDUCTOR (in.) | | FINISHED WIRE | | |
|-------------------|--------------------|---------------------------------------|---|---------|--|----------------|-------------------------------|
| | | | MINIMUM | MAXIMUM | MAXIMUM RESISTANCE AT 20°C (ohms/1000 ft) | DIAMETER (in.) | MAXIMUM WEIGHT (lbs/1000 ft.) |
| | | | | | | | |
| 55FA0511-22-* | 22 | 19 x 34 | .029 | .033 | 16.2 | .051 ± .003 | 4.0 |
| 55FA0511-20-* | 20 | 19 x 32 | .037 | .041 | 9.88 | .059 ± .003 | 5.8 |
| 55FA0511-18-* | 18 | 19 x 30 | .046 | .051 | 6.23 | .070 ± .003 | 8.7 |
| 55FA0511-16-* | 16 | 19 x 29 | .052 | .058 | 4.81 | .078 ± .004 | 11.2 |
| 55FA0511-14-* | 14 | 19 x 27 | .065 | .073 | 3.06 | .095 ± .004 | 16.1 |
| 55FA0511-12-* | 12 | 37 x 28 | .084 | .090 | 2.02 | .112 ± .004 | 24.0 |
| 55FA0511-10-* | 10 | 37 x 26 | .106 | .114 | 1.26 | .136 ± .005 | 37.0 |

TABLE II. PERFORMANCE DETAILS

| PART NUMBER 1/ | BEND TESTING | | | |
|-------------------|---|-----------|---|-----------|
| | MANDREL DIAMETER (inch) (± 3%) | | WEIGHT (lb) (± 3%) | |
| | IMMERSION, LIFE CYCLE AND CROSSLINKING PROOF TEST | COLD BEND | IMMERSION, LIFE CYCLE AND CROSSLINKING PROOF TEST | COLD BEND |
| 55FA0511-22-* | .500 | 2.00 | .750 | 3.00 |
| 55FA0511-20-* | .750 | 2.50 | 1.25 | 4.00 |
| 55FA0511-18-* | 1.00 | 3.00 | 1.75 | 4.00 |
| 55FA0511-16-* | 1.00 | 3.00 | 2.00 | 5.00 |
| 55FA0511-14-* | 1.00 | 5.00 | 2.00 | 5.00 |
| 55FA0511-12-* | 1.50 | 6.00 | 2.50 | 5.00 |
| 55FA0511-10-* | 1.50 | 8.00 | 2.50 | 5.00 |

This product meets or exceeds all requirements of SAE AS85485/9, less identification, for AWG's 22-10. All other AWG sizes meet or exceed requirements of SAE AS85485, less identification.

Users should evaluate the suitability of this product for their application. Specifications are subject to change without notice. Tyco Electronics also reserves the right to make changes in materials or processing, which do not affect compliance with any specification, without notification to Buyer.

1/ COLORS AND COLOR CODE DESIGNATORS SHALL BE IN ACCORDANCE WITH MIL-STD-681. OTHER CODES AND SUFFIXES MAY BE ADDED TO THE PART NUMBER. AS NECESSARY, TO CAPTURE ANY ADDITIONAL REQUIREMENTS IMPOSED BY THE PURCHASE ORDER.

| | | | |
|-------------|---|--|---|
| Page 1 of 3 | The TE logo, Tyco Electronics, Electroloss and Raychem are trademarks. | | Raychem Wire & Cable 501 Oakside Avenue Redwood City, CA 94063-3800 Phone: 1-800-227-8816 Fax: 1-650-361-6297 |
| | DIMENSIONS ARE IN INCHES, AND UNLESS OTHERWISE DESIGNATED ARE NOMINAL | | |
| | THIS SPECIFICATION SHEET TAKES PRECEDENCE OVER DOCUMENTS REFERENCED HEREIN. REFERENCED DOCUMENTS SHALL BE OF THE ISSUE IN EFFECT ON DATE OF INVITATION FOR BID. | | |

| | | | | |
|---|--------------------------------------|-------------|---------------|-------------------------------|
|  | SPECIFICATION CONTROL DRAWING | Page 2 of 3 | Revision J | SCD Number 55FA0511 |
|---|--------------------------------------|-------------|---------------|-------------------------------|

WIRE RATINGS AND ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 150°C

Maximum continuous conductor temperature

VOLTAGE RATING: 600 volts (rms) at sea level

ATTENUATION (INSERTION LOSS): See Table III

BLOCKING: 200 ± 3°C for 6 hours

COLOR: Light violet preferred

CONCENTRICITY: Primary Insulation - 50% (minimum); Finished Wire - 70% (minimum)

CROSSLINKING PROOF TEST: 300 ± 3°C for 7 hours

FLAMMABILITY: 3 seconds (maximum); 3 in. (maximum); no flaming of facial tissue

FLUORIDE EXTRACTION: 70 ± 2°C for 168 hours, 150 ppm (maximum)

HUMIDITY RESISTANCE: Insulation Resistance, 5000 megohms for 1000 ft. (minimum)

IDENTIFICATION AND COLOR STRIPING DURABILITY:

125 cycles (250 strokes) (minimum), 500 g weight

IMMERSION: Diameter increase 5% (maximum); no cracking, no dielectric breakdown

INSULATION ELONGATION AND TENSILE STRENGTH:

Primary Insulation, Filter Layer and Primary Jacket pulled together

Elongation, 50% (minimum)

Tensile Strength, 3000 lbf/in² (minimum)

INSULATION FLAWS:

Primary Insulation only,

Spark Test, 1.5 kV (rms) at 60 Hz

4.2 kV (rms) at 3 kHz

Impulse Dielectric Test, 6.0 kV (peak)

Finished Wire,

Spark Test, 3.0 kV (rms) at 60 Hz

5.7 kV (rms) at 3 kHz

Impulse Dielectric Test, 8.0 kV (peak)

INSULATION RESISTANCE: 5000 megohms for 1000 ft. (minimum)

INSULATION THICKNESS:

Primary Insulation, .002 in. (minimum);

Filter Layer, average .0025 in. (minimum);

Primary Jacket, .0035 in. (minimum)

LIFE CYCLE: 200 ± 3°C for 168 hours

LOW TEMPERATURE-COLD BEND: -65 ± 2°C for 4 hours

SHRINKAGE: 200 ± 3°C for 6 hours, 0.125 in. (maximum)

SMOKE: 200 ± 2°C, no visible smoke

SURFACE RESISTANCE: 500 megohms-in. (minimum), initial and final readings

THERMAL SHOCK RESISTANCE: 150 ± 3°C, .060 in. (maximum)

THERMAL STABILITY: 180 ± 3°C for 1250 hours

VOLTAGE WITHSTAND (Post Environmental): 1500 volts (rms), 60 Hz

WRAP TEST: 200 ± 3°C for 6 hours, no cracking


PART NUMBER:

The "*" in the part numbers in Tables I-III shall be replaced by a color code designator, except that violet shall be light violet and designator shall be 7L.

1/ Example: AWG 20, light violet: 55FA0511-20-7L

AWG 20, light violet with blue stripe: 55FA0511-20-7L6

1/ See footer section on page 1

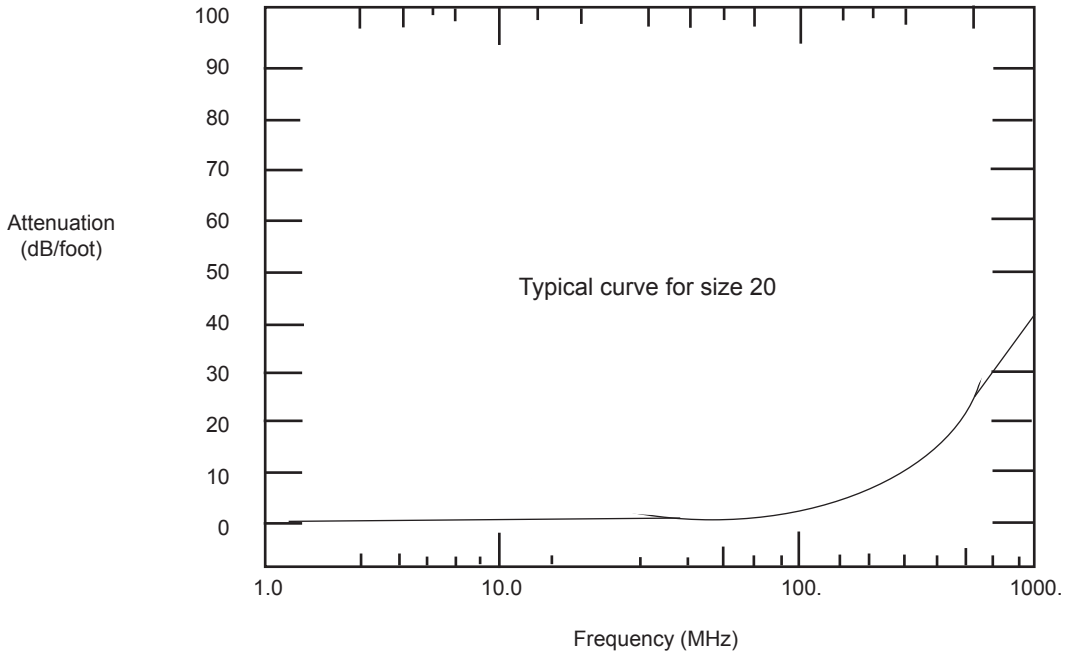

ATTENUATION (INSERTION LOSS)

| TABLE III. ATTENUATION (INSERTION LOSS) + | | | | | | | |
|---|-----------------------|----------|-------|-----------------------------|---------|----------|-----------------------|
| PART NUMBER 1/ | PASS BAND (dB/ft.) | | | TRANSITION BAND (dB/ft.) | | | STOP BAND (dB/ft.) |
| | 1.0 MHz | 10.0 MHz | | 100 MHz | 500 MHz | 1000 MHz | 1 to 12 GHz |
| | (max) | (min) | (max) | (min) | (min) | (min) | (min) |
| 55FA0511-22-* | .02 | .06 | 0.20 | 1.3 | 12 | 30 | 30 |
| 55FA0511-20-* | .02 | .06 | 0.20 | 1.3 | 12 | 30 | 30 |
| 55FA0511-18-* | .02 | .06 | 0.20 | 1.3 | 13 | 33 | 33 |
| 55FA0511-16-* | .02 | .06 | 0.20 | 1.3 | 13 | 33 | 33 |
| 55FA0511-14-* | .02 | .06 | 0.20 | 1.3 | 13 | 33 | 33 |
| 55FA0511-12-* | .02 | .04 | 0.20 | 1.3 | 12 | 30 | 30 |
| 55FA0511-10-* | .02 | .04 | 0.20 | 1.3 | 12 | 30 | 30 |

1/ See footer section on page 1

+ THE PRIMARY WIRE OF THIS SPECIFICATION SHEET SHALL MEET THE ATTENUATION REQUIREMENTS SHOWN ABOVE ONLY WHEN USED AS A SINGLE COMPONENT IN A SHIELDED CABLE.



Компания «ЭлектроПласт» предлагает заключение долгосрочных отношений при поставках импортных электронных компонентов на взаимовыгодных условиях!

Наши преимущества:

- Оперативные поставки широкого спектра электронных компонентов отечественного и импортного производства напрямую от производителей и с крупнейших мировых складов;
- Поставка более 17-ти миллионов наименований электронных компонентов;
- Поставка сложных, дефицитных, либо снятых с производства позиций;
- Оперативные сроки поставки под заказ (от 5 рабочих дней);
- Экспресс доставка в любую точку России;
- Техническая поддержка проекта, помощь в подборе аналогов, поставка прототипов;
- Система менеджмента качества сертифицирована по Международному стандарту ISO 9001;
- Лицензия ФСБ на осуществление работ с использованием сведений, составляющих государственную тайну;
- Поставка специализированных компонентов (Xilinx, Altera, Analog Devices, Intersil, Interpoint, Microsemi, Aeroflex, Peregrine, Syfer, Eurofarad, Texas Instrument, Miteq, Cobham, E2V, MA-COM, Hittite, Mini-Circuits, General Dynamics и др.);

Помимо этого, одним из направлений компании «ЭлектроПласт» является направление «Источники питания». Мы предлагаем Вам помощь Конструкторского отдела:

- Подбор оптимального решения, техническое обоснование при выборе компонента;
- Подбор аналогов;
- Консультации по применению компонента;
- Поставка образцов и прототипов;
- Техническая поддержка проекта;
- Защита от снятия компонента с производства.



Как с нами связаться

Телефон: 8 (812) 309 58 32 (многоканальный)

Факс: 8 (812) 320-02-42

Электронная почта: org@eplast1.ru

Адрес: 198099, г. Санкт-Петербург, ул. Калинина, дом 2, корпус 4, литера А.